

Ruthenocuprates: Intrinsic magnetic multilayers

I. Živković,¹ Y.Hirai,² B.H.Frazer,² M.Prestor,^{1,*} D.Drobac,¹
D.Ariosa,³ G.Margaritondo,³ I.Felner,⁴ and M.Onellion^{2,†}

¹*Institute of Physics, P.O.B.304, HR-10 000, Zagreb, Croatia*

²*Physics Department, University of Wisconsin, Madison, WI 53706, U.S.A.*

³*Institut de Physique Appliquée, École Polytechnique Fédérale de Lausanne, CH-1012 Lausanne, Switzerland*

⁴*Racah Institute of Physics, Hebrew University, Jerusalem, Israel*

(Dated: February 1, 2008)

We report ac susceptibility measurements on polycrystalline samples of $SrRuO_3$ and three ruthenocuprates: superconducting $RuSr_2GdCu_2O_8$ (Ru-1212), superconducting $RuSr_2Eu_{2-x}Ce_xCu_2O_y$ (Ru-1222, $x=0.5$) and nonsuperconducting, insulating $RuSr_2Eu_{2-x}Ce_xCu_2O_z$ (Ru-1222, $x=1.0$). Ac susceptibility of both Ru-1222 compositions exhibit logarithmic time relaxation and ‘inverted’ hysteresis loops. Ru-1212 samples exhibit none of these behaviors. We interpret the magnetic behavior of Ru-1222 in the framework of weakly coupled magnetic multilayers and argue that superconductivity coexists with qualitatively different magnetic behaviors.

PACS numbers: 74.27.Jt, 74.25.Ha, 75.60.Lr, 75.70.Cn

The coexistence of superconductivity and long-range magnetic order, and the types of magnetic order compatible with superconductivity, have long been of interest [1]. For ruthenocuprate samples, the precise type of the long-range magnetic order coexisting with superconductivity [2, 3] remains controversial and intriguing [4, 5]. In this report we find that superconductivity coexists with qualitatively different magnetic behavior within the ruthenocuprate family. The main result of this report is that the Ru-1222 ruthenocuprates exhibit unexpected magnetic properties: By studying ac susceptibility in step-like and continuously sweeping low magnetic fields we report a pronounced susceptibility switching, logarithmic time relaxations (magnetic aftereffect) and hysteretic, inverted-in-sense, susceptibility butterfly loops. Most of these properties have been individually reported previously in other, nonsuperconducting, magnetic systems, but the Ru-1222 ruthenocuprates exhibits all of these properties. In marked contrast, superconducting Ru-1212 samples exhibit none of these properties. We argue that Ru-1222 samples are intrinsic magnetic multilayers, and provide a model for the magnetic coupling.

Polycrystalline samples were fabricated as published elsewhere [2]. We fabricated $SrRuO_3$ polycrystalline samples to serve as a three dimensional itinerant ferromagnet reference material. Ac susceptibility measurements were performed using a CryoBIND system [6]. An ac frequency of 230 Hz and an ac magnetic field amplitude of 0.15 Oe were typically used. A dc magnetic field amplitude up to 100 Oe was also used. Fig.1 shows, from ac susceptibility data, that there are significant differences in magnetic ordering of Ru-1212 and Ru-1222 sample families. While Ru-1212 is characterized by a single maximum at $T_N = 133K$, ac susceptibility of Ru-1222

samples exhibit a peak at T_M ($=85K$ or $117K$, for $x=0.5$ and $x=1.0$ samples) and a less pronounced feature in the temperature range $120-140K$ (detailed shape depends on x), followed by anomalous susceptibility behavior extending up to $180K$. Neutron diffraction studies [4] of Ru-1212 indicate that the sharp ac susceptibility maximum at T_N corresponds to the onset of antiferromagnetic long range order of the Ru moments. Magnetization studies establish that there is also a ferromagnetic component of magnetic order, usually attributed to weak ferromagnetism of canted Ru moments [2]. Assigning a precise interpretation to each particular anomaly is not straightforward [7] and will be, as well as obviously important role of Ce in magnetic ordering (Fig.1), a subject of separate publication. In this Letter we focus primarily the temperature range of susceptibility maxima of the Ru-1222 family

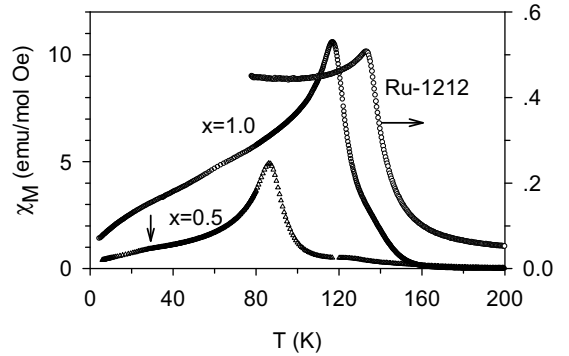


FIG. 1: Ac susceptibility measurements of Ru-1222 ($x=0.5$ and $x=1.0$) and Ru-1212 samples. Note different scales for the two sample types. Vertical arrow indicates superconducting transition.

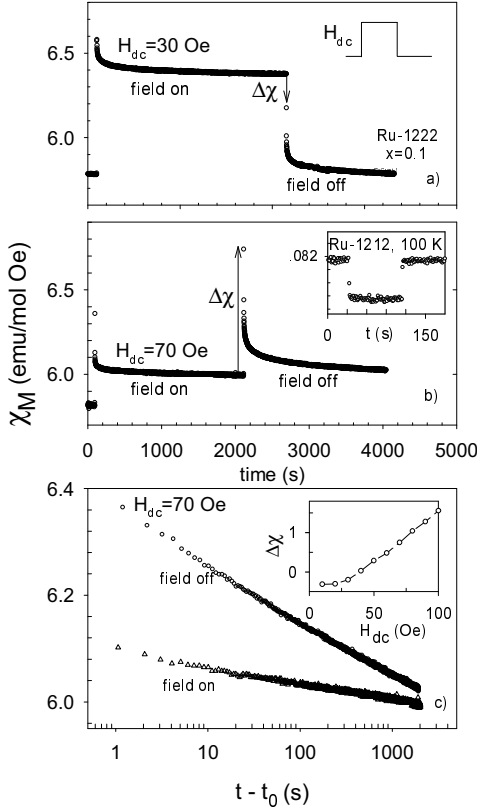


FIG. 2: a) Ac susceptibility versus time for Ru-1222, $x=1.0$ at 80K, with $H_{dc} = 0\text{Oe}$ initially, then $H_{dc} = 30\text{Oe}$, and finally $H_{dc} = 0\text{Oe}$, shown schematically in the Inset. ($\Delta\chi$), defined as change in susceptibility immediately after H_{dc} is switched off, is negative. Note relaxation of susceptibility. b) All conditions the same as in a) except $H_{dc} = 70\text{Oe}$. ($\Delta\chi$) is positive for this value of H_{dc} . Note relaxation of susceptibility. Inset: Analogous data for Ru-1212. Vertical scale is arbitrary units. Note absence of relaxation. (c) Ac susceptibility versus logarithm of time for Ru-1222, $x=1.0$, with $H_{dc} = 70\text{Oe}$ and 80K. (t_0) is time at which H_{dc} is either switched on or off. Data for both field on and field off conditions included. Inset: Overshoot $\Delta\chi$ (in units of emu/moleOe) at 80K versus H_{dc} . Note change from negative (no overshoot) to positive (overshoot) at $H_{dc} \approx H_{sf}$.

and report on important new aspects characterizing the complex magnetic order. The Ru-1222 samples of both compositions ($x=0.5$, superconductor, and $x=1.0$, insulator) exhibit qualitatively similar behavior. Quantitatively, the effects are more pronounced in $x=1.0$ sample and Figs.2-4 show the results for this sample only. We first report on time relaxation measurements shown in Fig.2. In these experiments we monitor ac susceptibility of the zero-field-cooled (ZFC) sample in its response to the step-like changes (H_{dc}) of the dc magnetic field (Fig.2a, inset). Fig.2 shows the time dependence of ac susceptibility for two values of H_{dc} . The data indicate:

a) A step-like change of magnetic field causes i) ac susceptibility switch to a new value, and ii) a sudden

transformation of the equilibrium (ZFC) to a metastable magnetic state. The magnitude of the switch ($\Delta\chi$) (Fig. 2a, 2b) depends on H_{dc} , while its sign can be positive (for turning the field on) or it can be both negative and positive (for turning the field off). The field-induced metastable state is characterized by an ac susceptibility that relaxes in time, a phenomenon variously attributed to disaccommodation [8, 9] or, in wider context of relaxing magnetization, to magnetic aftereffect [10]. By contrast, there is no indication of time relaxation in Ru-1212 samples (Fig.2b, inset);

b) Relaxation is precisely logarithmic in time for both field on and off (Fig.2c), following the usual form $\chi(t) = \chi_0[1 - \alpha \ln(t - t_0)]$. The parameters, χ_0 and the relaxation rate α , depend on temperature, H_{dc} , and on the magnetic history (i.e., on whether the field has been turned on or turned off);

c) For $|H_{dc}|$ above a threshold value of $\approx 40\text{Oe}$, when H_{dc} is turned off there is a pronounced ‘overshoot’ phenomenon, i.e., a sizeable positive ($\Delta\chi$) (Fig.2b);

d) Applying a rectangular field pulse results in a magnetic state with, surprisingly, *increased* ac susceptibility (Fig.2b). This state is logarithmically metastable in time. The slow relaxation rate indicates the existence of the field-induced excited ac susceptibility for many time decades.

Next, we report the observation of inverted hysteresis phenomena. In measuring the magnetization hysteresis one ramps the applied magnetic field (H) from positive to negative and back and continuously measures the magnetization $M(H)$. In a similar, ‘butterfly’ hysteresis technique,[11] the ac susceptibility $\chi_{ac}(H)$, instead of magnetization, is measured. In general, these two hysteresis loops yield similar information.[12] For example, the characteristic maxima in butterfly hysteresis (Fig.3a and inset) correspond to the points in magnetization hysteresis satisfying $M(H) = 0$. Therefore, the positions of butterfly maxima define the coercive field [11]. Fig.3a shows typical butterfly hysteresis data taken for Ru-1222 and Ru-1212 samples. The data immediately establish that the two types of ruthenocuprates exhibit qualitatively different responses. Comparing the Ru-1222 data to the results characterizing the itinerant bulk ferromagnet $SrRuO_3$ (Inset to Fig.3a), there are also pronounced differences. The most striking difference is the inverted sense of loop circulation for Ru-1222: the susceptibility signal is consistently larger for the field- decreasing branch compared to the field- increasing branch. To our knowledge, this represents the first observation of the inverted butterfly loops in a bulk magnetic system.

The numerical integration of the butterfly hysteresis is shown in Fig.3b. While the result for $SrRuO_3$ exhibits the counter-clockwise pattern of the usual magnetization hysteresis (Fig.3b inset), the integrated butterfly of the Ru-1222 sample exhibit an inverted (clockwise) hysteresis loop. It is important to note that vibrating sample

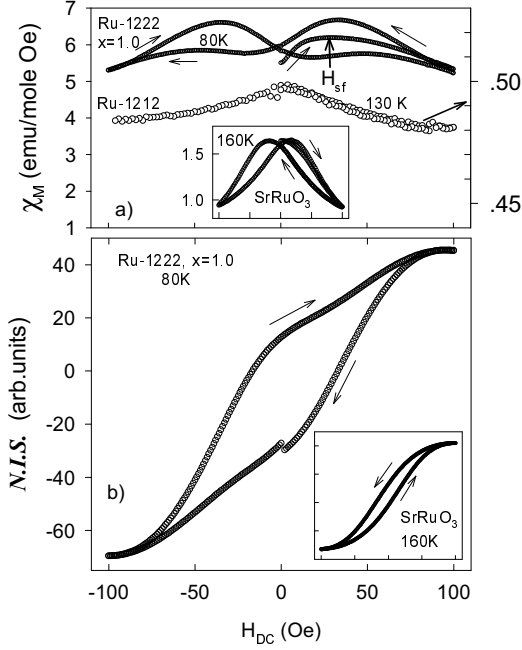


FIG. 3: a) Left axis: ‘Butterfly’ hysteresis for Ru-1222, $x=1.0$ at 80K. Right axis: Analogous data for Ru-1212, just below magnetic ordering temperature. Note just monotonous ac susceptibility decrease and no hysteresis. Inset: Butterfly hysteresis for $SrRuO_3$ at 160K ($T_c = 165K$). Note the response for increasing and decreasing H_{dc} are opposite to that of Ru-1222. b) Numerical integral NIS ($\equiv \int_0^H \chi(h)dh$) of butterfly susceptibility shown in a) versus H_{dc} for Ru-1222. Note the inverse hysteresis loop. Inset: NIS for $SrRuO_3$ at 160K. Note that this hysteresis corresponds, by all means, to the standard ferromagnetic one.

magnetometer measurements of the same samples, both $SrRuO_3$ and Ru-1222, (data not shown) show the dc magnetization hysteresis loop in the normal sense of circulation. Therefore, the inverted hysteresis phenomenon represents a unique feature of the Ru-1222 system, which arises from field-induced metastable states observed in magnetic aftereffect. Other noteworthy features of the Ru-1222 butterfly hysteresis are i) the presence of a maximum even in the initial ZFC (virgin) curve, ii) pronounced dependence on the observing time used to obtain the data, and iii) the presence of the two (instead of only one) maxima per field-ascending or -descending branch.

As shown in Fig.3a the virgin branch is characterized by a maximum formed at the characteristic field H_{sf} . In ferromagnets the virgin curve typically does not exhibit a maximum [13] because the remanence, and thus coercive field [11], builds up only after the first field swing, as seen in the $SrRuO_3$ results (Inset to Fig.3a). The quantitative size of the butterfly hysteresis loop depends on the observation time, another indicate that the metastable magnetic states are involved. Qualitatively, however, over the range of sweep times we studied- several minutes to

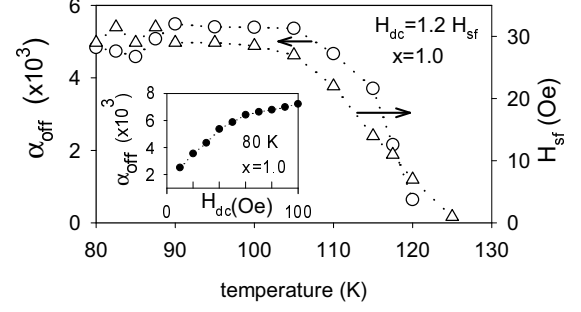


FIG. 4: Left axis: α_{off} , the relaxation rate constant defined in text, when H_{dc} is switched off, versus temperature. Right axis: The field attributed to spin flop, H_{sf} (Fig.3a), versus temperature. Note that both quantities are zero at temperatures above the susceptibility peak. Inset: α_{off} , at 80K, versus H_{dc} .

one day- the inverted butterfly loops exhibit the same features. It is further noteworthy that the field H_{sf} approximately coincides with the minimum field needed to apply in order to get closed butterfly loops: if the range of sweeping field was narrower than $(-H_{sf}, +H_{sf})$ no closed loops would be observed whatsoever.

Figs.2,3 illustrate two interesting phenomena- magnetic logarithmic relaxation (Fig.2) and inverted hysteretic behavior (Fig.3). Figure 4 shows that these two phenomena are related in the Ru-1222 system. Fig.4a illustrates the temperature dependence of H_{sf} (Fig.3) and of α , the logarithmic relaxation rate (Fig.2). It is noteworthy that the temperature dependence of these two parameters is virtually identical, indicating that they have a common origin. Another indication that the two phenomena are interrelated is shown in the inset of Fig.4a. Note that α changes rapidly at low fields, but saturates at a H_{dc} field value slightly above H_{sf} . Another quantity that qualitatively changes for fields close to H_{sf} is $\Delta\chi$, shown in Inset to Fig.2c. Above H_{sf} , $\Delta\chi$ becomes positive and just monotonously increases with H_{dc} . Again, these qualitative changes in relaxation parameters are connected to the inverse hysteretic behavior.

Now we interpret our results. Based on the feature of inverted hysteresis loops and on the presence and the properties of the field H_{sf} , we propose that the magnetism of weakly antiferromagnetically (AF) coupled magnetic multilayers [14] underlies the ordering in Ru-1222 for the temperature range around T_M . Further, based on the time relaxations, we argue that the weak AF coupling relies primarily on the long range dipole-dipole interaction: as it is well-known [15] this interaction may be responsible for slow, in particular logarithmic, relaxation without any additional assumptions. Our model stems from previous reports of inverted hysteresis loops, limited exclusively to magnetic multilayers [16] and nanoscale magnetic films [17]. Ref. 16 argued for ad-

jacent layers having co-existing magnetic moments, with AF-like coupling between adjacent layers. Ref. 16 also demonstrated that the inverted hysteresis loop behavior disappears if the AF coupling between adjacent layers is changed to ferromagnetic coupling. We argue that the inverted hysteresis loop data (Fig.3) indicates ferromagnetic intralayer and AF interlayer coupling. We further argue that the observed hysteretic behaviors actually originates from spin flop or spin flip processes by which the net magnetization [18] of adjacent, weakly antiferromagnetically coupled, RuO_2 layers increases. Compared to bulk antiferromagnets, however, the ruthenocuprate magnetic multilayer spin flop fields are weaker by several orders of magnitude (which is generally true for atomic-scale multilayers [18]), so the hysteresis loops approach saturation for fields of the order of 100 Oe. We attribute the maxima in the initial ac susceptibility data (Fig.3a) to a spin flop transition. This assignment is quite similar to a recent report on AF ordered chain-ladder compounds [19]. Our assignment is further supported by the fact that the dynamical hysteresis loops close only for applied fields higher than H_{sf} . Previous reports [2] indicate that the RuO_2 planes are the main source of magnetic moment for Ru-1222. Consistent with weak magnetic interactions of our model we argue that only a small interlayer component of canted Ru moments participates in ferromagnetic intralayer and AF interlayer coupling.

Logarithmic relaxations, considered independently from other observations, could perhaps be interpreted in framework of domain-wall stabilization (disaccommodation) involving a broad range of activation energies, as has recently been applied to observations in a perovskite-manganite [8]. However, one of us (IF) and colleagues have performed temperature-dependent x-ray diffraction studies of Ru-1222; these indicate no structural change-necessary for disaccommodation- with temperature [20]. Therefore, this model favors the active role of dipole-dipole interaction due to its consistency with both the inferred weak AF coupling [18] and the observed logarithmic relaxations [15].

In summary, we have reported data indicating that Ru-1222 exhibits qualitatively new magnetic behavior, including magnetic logarithmic relaxation, inverted hysteresis loops, and metastable magnetic states. However, superconductivity in the ruthenocuprates is consistent both with the presence of these metastable magnetic states in Ru-1222 and with the qualitatively different magnetic behavior of Ru-1212.

We benefited from conversations with Robert Joynt. Financial support was partially provided by the U.S.-Israel Binational Science Foundation, Fonds National Suisse, and EPFL.

* Electronic address: prester@ifs.hr

† Electronic address: onel-

lion@landau.physics.wisc.edu

- [1] *Superconductivity in Ternary Compounds*, edited by M.B.Maple and O.Fischer, Springer-Verlag, Berlin 1982.
- [2] I.Felner, U.Asaf, Y.Levi, and O.Millo, Phys.Rev.B 55 (1997) R3374.
- [3] C.Bernhard, et. al., Phys.Rev.B 59, 14099 (1999)
- [4] J.W.Lynn, et al. Phys.Rev.B 61 (2000) R14964
- [5] G.V.M.Williams and S.Kr  mer, Phys.Rev.B 62, 4132 (2000)
- [6] <http://www.cryobind.com>
- [7] There is pronounced deviation from Curie-Weiss (CW) model in the whole temperature range below 180K. More generally, the failure of CW model to determine the magnetic ground state of Ru-1212 demonstrates a questionable validity of this simple mean field model in interpretation of complex magnetic systems, such as ruthenocuprates.
- [8] M.Muroi, R.Street, J.W.Cochrane, and G.J.Russell, Phys.Rev.B 62 (2000) R9268
- [9] H.Kronm  ller, Philos.Mag. B48 (1983) 127
- [10] R.Street and S.D.Brown, J.Appl.Phys. 76 (1994) 6386.
- [11] F.H.Salas and D.Weller, JMMM 128 (1993) 209, and references therein.
- [12] The equivalency of butterfly and magnetization hysteresis is a simple consequence of the relationship: $M(H) = \int_0^H \chi(h)dh$ valid - up to an integration constant- in simple isotropic ferromagnets. However, in complex magnetic systems replacing χ (a tensor) by a scalar is not approved and the relationship does not hold.
- [13] In principle, the observed maximum could be ascribed to a cross over between reversible and irreversible dynamics of ferromagnetic domains. However, the idea of reversibility, at least in its elementary form, is incompatible with logarithmic relaxations characterizing the whole 0-100 Oe range. Therefore, it seems that the latter interpretation cannot be applied in its original transparent form.
- [14] G.A.Prinz, Science 282 (1998) 1660, and references therein.
- [15] D.K.Lottis, R.M.White, and E.D.Dahlberg, Phys.Rev.Lett.67 (1991) 362;
- [16] P.Pouloupoulos, R.Krishnan, and N.K.Flevaris, JMMM 163 (1996) 27, and references therein.
- [17] M.Cougo dos Santos, et al., Phys.Rev.B 61 (2000) 1311
- [18] B.Dieny, J.P. Gavigan, and J.P.Rebouillat, J.Phys.:Condens.Matter 2 (1990) 159
- [19] M.Isobe, Y.Uchida, and E.Takayama-Muromachi, Phys.Rev.B 59 (1999) 8703.
- [20] I. Felner et al. Physica C (in press).